

ADA081344

A060728 ARACOR



LEVEL III

IMPROVEMENT IN GaAs DEVICE YIELD AND PERFORMANCE  
THROUGH SUBSTRATE DEFECT GETTERING

INTERIM TECHNICAL REPORT

PREPARED FOR:

DEFENSE ADVANCED RESEARCH PROJECTS AGENCY  
1400 WILSON BOULEVARD  
ARLINGTON, VIRGINIA 22209

ATTENTION: DR. RICHARD A. REYNOLDS

MONITORED BY:

OFFICE OF NAVAL RESEARCH  
DEPARTMENT OF THE NAVY  
800 NORTH QUINCY STREET  
ARLINGTON, VIRGINIA 22217

DTIC  
ELECTE  
S FEB 27 1980 D  
A

DISTRIBUTION STATEMENT A

Approved for public release;  
Distribution Unlimited

ADVANCED RESEARCH AND APPLICATIONS CORPORATION

80 2 26 067

DOC FILE COPY

# ARACOR



**IMPROVEMENT IN GaAs DEVICE YIELD AND PERFORMANCE  
THROUGH SUBSTRATE DEFECT GETTERING**

**Interim Technical Report**

**Prepared by:**

**T. J. Magee, J. Peng, J. Hong and R. A. Armistead**

**January, 1980**

**Sponsored by:**

**DEFENSE ADVANCED RESEARCH PROJECTS AGENCY  
1400 Wilson Boulevard  
Arlington, Virginia 22209**

**Attention: Dr. Richard A. Reynolds**

**Monitored by:**

**OFFICE OF NAVAL RESEARCH  
DEPARTMENT OF THE NAVY  
800 North Quincy Street  
Arlington, Virginia 22217**

**ADVANCED RESEARCH AND APPLICATIONS CORPORATION**

1223 E. Arques Avenue, Sunnyvale, California 94086 (408) 733-7780

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER NR 243-022-012	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER <b>①</b>
4. TITLE (and Subtitle) <b>②</b> Improvement in GaAs Device Yield and Performance Through Substrate Defect Gettering		5. TYPE OF REPORT & PERIOD COVERED Interim Technical Report
7. AUTHOR(s) <b>③</b> T. J. Magee, J. Peng, J. Hong, R. A. Armistead		6. PERFORMING ORG. REPORT NUMBER ARACOR Report No. TR-19-2
9. PERFORMING ORGANIZATION NAME AND ADDRESS Advanced Research and Applications Corporation 1223 East Arques Avenue Sunnyvale, California 94086 <b>393 004</b>		8. CONTRACT OR GRANT NUMBER(s) N00014-78-C-0065
11. CONTROLLING OFFICE NAME AND ADDRESS Advanced Research Projects Agency Materials Sciences Office 1400 Wilson Boulevard, Arlington, VA 22209		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS PE61101E 8D19 <b>ARPA Order-3516</b>
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) Office of Naval Research Code N00014, M. Yoder Arlington, Virginia <b>⑫ 426</b>		13. REPORT DATE January 1980
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		15. SECURITY CLASS (of this report) Unclassified <b>393 004</b>
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
18. SUPPLEMENTARY NOTES ONR Scientific Officer: Telephone (202) 696-4218		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Gallium arsenide      Au diffusion      Field effect transistors Defect gettering      Dislocation structure Impurity gettering      Ion implantation Epitaxy      Encapsulants Cr diffusion      Annealing		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The gettering of Cr and front-surfaces defects by mechanically produced back-surface damage in semi-insulating GaAs wafers has been investigated. It has been shown that improved VPE layers can be grown on pre-gettered substrates. Also, the level of Cr outdiffusing from the substrate during epilayer growth and subsequent annealing is substantially reduced when pre-gettered substrates are used. Thermal stability times of back-surface damage at an anneal temperature of 800°C is typically on the order of 2 - 3 hours, corresponding to the point		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)



Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

✓  
at which major back-surface microstructural damage is largely annealed. Increases in the thermal stability period were attained by encapsulating the back surface with an As-doped SiO<sub>2</sub> layer. Subsequent investigations of Au contacts on GaAs showed that Cr was mobile during 350°C alloying, resulting in gettering within alloy damage regions and subsequent outdiffusion into the Au film.

Device structures (FET) fabricated on VPE layers on pre-gettered GaAs wafers showed considerable improvements in both yield/wafer, noise figures at higher frequencies and input capacitance values.

Accession for	
NTIS GAI	<input checked="" type="checkbox"/>
DDC TAB	
Unannounced	
Justification	
By	
Distribution/	
Availability Codes	
Dist.	Avail and/or special
A	

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

## CONTENTS

	Page
1. Introduction . . . . .	1
1.1 Background . . . . .	1
1.2 Summary of Results . . . . .	1
1.3 Publications . . . . .	2
2. Gettering of Cr by Back-Surface Mechanical Damage. . . . .	3
2.1 Experimental Procedure . . . . .	3
2.2 Results . . . . .	4
2.2.1 Transmission Electron Microscopy . . . . .	4
2.2.2 Secondary Ion Mass Spectrometry . . . . .	6
3. Back-Surface Gettering and Cr Outdiffusion in VPE GaAs Layers . . . . .	10
3.1 Experimental Procedure . . . . .	10
3.2 Results . . . . .	11
4. Alloying of Au Layers and Redistribution of Cr in GaAs . . 18	
4.1 Experimental . . . . .	18
4.2 Results . . . . .	19
5. Performance of FET Structures Fabricated in VPE Layers on Pre-Gettered Substrates . . . . .	25
6. Conclusions and Future Experiments . . . . .	31
References. . . . .	32
Distribution List . . . . .	34

# FIGURES

Page

Figure 1.	Transmission Electron Micrographs of Back-Surface-Damaged Wafers After Annealing; a) 30 min; b) 180 min. . .	5
Figure 2.	SIMS Profiles of Back-Surface Gettered Cr in GaAs Wafers; a) Control (no induced damage), Cu-doped, annealed 800°C, 1 hr; b) Cr-doped, annealed 800°C, 0.5 hr; c) Cr-doped, annealed 800°C, 2.5 hr; d) Si-doped, Cr layer (front), annealed 800°C, 1 hr. . . .	7
Figure 3.	Defect Density and Cr Concentration Profiles of Back-Surface-Damaged Annealed GaAs Substrates. . . .	12
Figure 4.	Optical Micrographs of Etch Figures of Annealed Samples; a) Control; b) Gettered. . . . .	14
Figure 5.	SIMS Profiles of Cr Concentration in Substrates and VPE Layers After Deposition and Annealing; a) After deposition; b) 800°C post deposition anneal ( $t_{VPE}=1.7$ m) . . . . .	16
Figure 6.	Transmission Electron Micrograph of GaAs Under (1000Å thick) Au Contact Layer After Annealing at 350°C For 1 Minute. . . . .	21
Figure 7.	SIMS Profiles of (1000Å Au/GaAs Structure After Annealing at 350°C; a) $t_A=1$ min; b) $t_A=3$ min; c) $t_A=10$ min.. . . .	22
Figure 8.	SIMS Profiles of (4000Å) Au/GaAs Structure After Annealing at 350°C; a) $t_A=1$ min; b) $t_A=10$ min.. . . .	24
Figure 9.	Profile-VPE/GaAs (Control) Sample.. . . .	26
Figure 10.	Profile-VPE/GaAs (Pre-gettered) Sample. . . . .	27

## TABLES

	Page
Table 1. Device Data - Control (Ungettered) Substrate. . . . .	28
Table 2. Device Data - Pre-gettered Substrate. . . . .	29

## 1. INTRODUCTION

### 1.1 Background

In this research program, it has been shown that mechanical and ion-implantation-induced damage at the back surface of GaAs wafers can be effectively used to getter front-surface defects and heavy metal impurities from the bulk material. It was demonstrated that the mechanical damage process could be optimized to produce maximum gettering efficiencies both in terms of front-surface defect annihilation and removal of mobile Cr from the interior of the sample. Comparative analyses of back-surface ion-implanted and mechanically-damaged wafers showed that the rotary abrasive (mechanical) technique was superior to the ion-implantation method for gettering in GaAs in terms of defect/impurity removal rate, back-surface damage retention time, and reverse annealing or "de-gettering" characteristics.

Recent experiments were directed to extending the investigation of defect and impurity gettering in GaAs, with particular emphasis on the gettering of mobile Cr over a wide range of annealing temperatures. The back-surface-gettering technique was then used as a means of improving substrates for growth of epitaxial layers on semi-insulating wafers and as a step introduced in the process line for production of GaAs-FET device structures.

### 1.2 Summary of Results

The results of investigations conducted during this reporting period are described briefly in the sections to follow.

- o Analysis and identification of Cr gettering and reverse annealing effects by back-surface-damage regions.
- o Improvement in back-surface-damage stability times using an As-doped SiO<sub>2</sub> encapsulation layer on the back of the wafer.
- o Identification of Cr gettering and outdiffusion during alloying (350°C) of contact structures on GaAs.



- o Growth of low-defect-concentration VPE layers on back-surface (pre-gettered) Cr-doped substrates.
- o Reduction of Cr outdiffusion into VPE layers grown on pre-gettered Cr-doped substrates.
- o Improved electrical properties of VPE layers on Cr-doped substrates.
- o Improvement in the electrical parameters and the device yield of FET structures fabricated in VPE layers on pre-gettered (Cr-doped) substrates.
- o Identification of low temperature ( $\leq 350^{\circ}\text{C}$ ) Cr-gettering in GaAs.

### 1.3 Publications

The following research publications were drawn in part or in total from this program of research.

- a) "Back-Surface Gettering and Cr Out-Diffusion in VPE GaAs Layers," Appl. Phys. Lett. 35, 277 (1979).
- b) "Alloying of Au Layers and Redistribution of Cr in GaAs," Appl. Phys. Lett. 35, 615 (1979).
- c) "Gettering of Au by Back-Surface Damage in GaAs," Phys. Stat. Sol. (A) 55, 161 (1979).
- d) "Back-Surface Gettering of Cr in GaAs," Phys. Stat. Sol (A) 55, 169 (1979).
- e) "Outdiffusion of Cr in VPE GaAs Layers and Back-Surface Gettering," Extended Abstracts, Vol. 79-2, ECS Meeting, Los Angeles, CA , October 14-19, 1979.

## 2. GETTERING OF Cr BY BACK-SURFACE MECHANICAL DAMAGE

Gettering of impurities in Si by ion-implantation-induced damage or mechanical damage has been reported<sup>1-6</sup> by a number of investigators. In contrast, there have been few detailed studies of impurity gettering by back-surface damage in GaAs. Recently, it was shown<sup>7</sup> by the present authors that Au impurities could be effectively gettered by dislocation lines introduced into the back surface of GaAs wafers. The Au was observed in the form of precipitates pinned along dislocation lines that extended to a depth of  $\approx 1.5 \mu\text{m}$  below the level of damage grooves at the back surface. Correlated transmission electron microscopy (TEM) and secondary ion mass spectrometry (SIMS) data showed the gettering process to be effective for annealing periods not exceeding the thermal stability time, or the time in which major microstructural damage is largely annihilated by annealing at a fixed temperature.

Preliminary studies by the authors have shown that Cr can also be gettered by mechanical or ion implantation damage in GaAs.<sup>8</sup> The purpose of these investigations was to extend the previous studies and to determine the gettering behavior of Cr as a function of annealing duration for variable periods, approaching the thermal stability time at  $800^\circ\text{C}$ .

### 2.1 Experimental Procedure

The gallium arsenide samples used in these experiments were obtained from Crystal Specialties Inc. and Monsanto Corporation. The wafers were of (100) orientation ( $+1^\circ$ ) and doped with Si or Cr to levels of  $0.008 \Omega\text{-cm}$  and  $10^8 \Omega\text{-cm}$ , respectively. Mechanical damage was introduced at the back surfaces using a  $30\text{-}\mu\text{m}$  particle size and a rotary abrasive technique described elsewhere.<sup>7</sup> All anneals were subsequently done in flowing  $\text{H}_2$  at  $800^\circ\text{C}$  for periods of 0.5 to 6 hours. Samples for TEM analysis were prepared by conventional jet thinning and sectioning techniques on  $2.5\text{-mm} \times 2.5\text{-mm}$  specimens. Bright- and dark-field electron microscopy was used in all cases to examine the structure of control, damaged and annealed samples.

Secondary ion mass spectrometry was used to obtain Cr impurity concentration profiles at the back surfaces of control and back surface damaged, annealed samples. To obtain calibration data for these experiments, GaAs and Si samples were simultaneously ion implanted with Cr and the integrated Cr content measured in the Si by nuclear back scattering techniques.<sup>9</sup> These data were then used to convert the measured Cr signals from SIMS profiles on GaAs and the resulting data correlated with predicted LSS (as-implanted) profiles.


## 2.2 Results

### 2.2.1 Transmission Electron Microscopy


Samples were subjected to rotary back-surface abrasion using a 30- $\mu$ m particle size, 8000 rpm rotation rate and a total contact time of 30 sec. Specimens were then examined in the electron microscope and micro-structural damage found in the form of laterally continuous forested dislocation nests extending to a distance of  $\approx 1.5 \mu$ m below the depth of damage grooves at the back surface, in agreement with previous results.<sup>7</sup>

Dislocation line structure was observed to be largely annealed after heating for 2 - 3 hours in flowing  $H_2$  at 800°C. Some residual dislocation line structure was found to persist up to anneal periods of 6 hours, but the fractional amount of damage remaining after 3 hours was typically  $\leq 10\%$  of the initial dislocation line content.

Figure 1 shows a series of bright-field electron micrographs obtained at the back surfaces of Cr-doped samples subjected to back-surface damage and subsequently annealed at 800°C for variable periods. It can be observed that the concentration of dislocation lines is considerably reduced as a function of increasing anneal time. Of particular importance, however, is the apparent absence of any identifiable precipitates or impurity segregation sites, either at the edges of dislocation lines or in isolated zones. This result is in sharp contrast to the previous results in which Au was shown reproducibly to nucleate in the form of precipitates pinned along dislocation lines. In all cases, we were unable to clearly

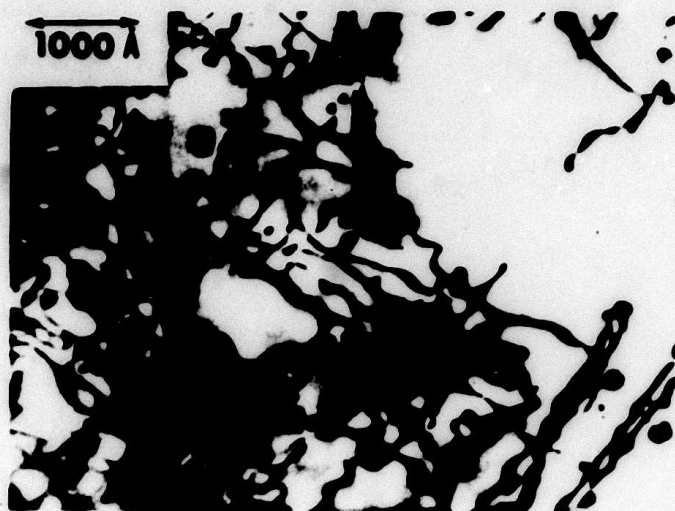

[a]

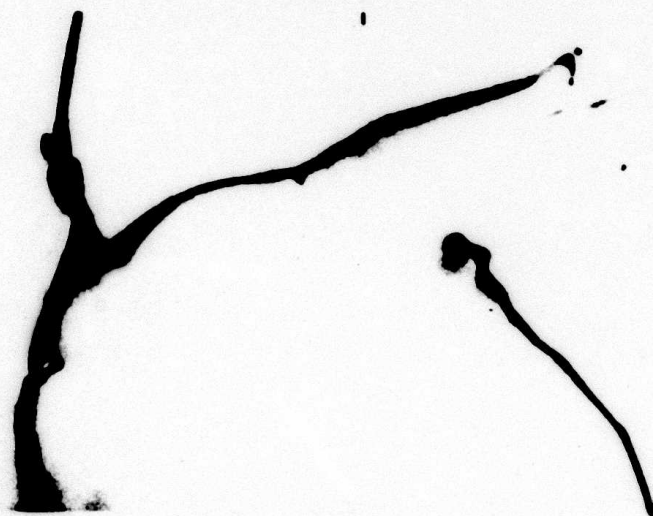

[b]

FIGURE 1. TRANSMISSION ELECTRON MICROGRAPHS OF BACK-SURFACE DAMAGED WAFERS AFTER ANNEALING; 2) 30 mn; b) 180 min.

identify precipitates in the back-surface damages and annealed Cr-doped samples. From these results, we can infer an absence of Cr precipitation along dislocation lines or a relatively weak strain field from small Cr segregation zones that do not permit adequate resolution to TEM.

To further investigate the possibility of Cr precipitation within the damaged regions, a series of experiments was conducted on selected Si-doped samples shown by SIMS to contain small (unintentional) Cr-doping concentrations of  $\leq 10^{16} \text{ cm}^{-3}$ . Chromium layers of 2- $\mu\text{m}$  thickness were then deposited on the front surfaces by an electroless technique and the uniformity checked by SEM examination. The samples were then heated in flowing  $\text{H}_2$  at  $800^\circ\text{C}$  for variable periods, as in the previous experiments, and the samples examined at the back surface in the TEM. The micrographs obtained were essentially identical to those shown in Figure 1 and no Cr precipitation was detected, although gettered Cr was clearly detectable by SIMS, as will be discussed in the next section.

#### 2.2.2 Secondary Ion Mass Spectrometry

Figure 2 shows SIMS profiles obtained at the back surfaces of Cr-doped control and mechanically-damaged GaAs samples subjected to anneals at  $800^\circ\text{C}$  for variable periods. Also shown for comparison is a representative profile obtained from an annealed, Si-doped (back-surface-damaged) GaAs sample containing a  $\approx 2\text{-}\mu\text{m}$  thick Cr layer on the front surface. All SIMS profiles were obtained within homogeneous damage distribution zones at the back surface.

Control (undamaged) samples subjected to  $800^\circ\text{C}$  anneals typically show a narrow region of Cr accumulation at the back surface. This is presently thought to be attributable to a slight gettering effect caused by the presence of small amounts of residual defects retained after chemical/mechanical polishing. After annealing of the back surface damaged samples for 1/2 hour, we observe a significant concentration of Cr at the back surface. For all samples, we detected a graded distribution decreasing to background doping levels at depths of  $\approx 1.5 \mu\text{m}$ . After annealing for 2.5 hours, the level of gettered Cr is reduced and the concentration gradient



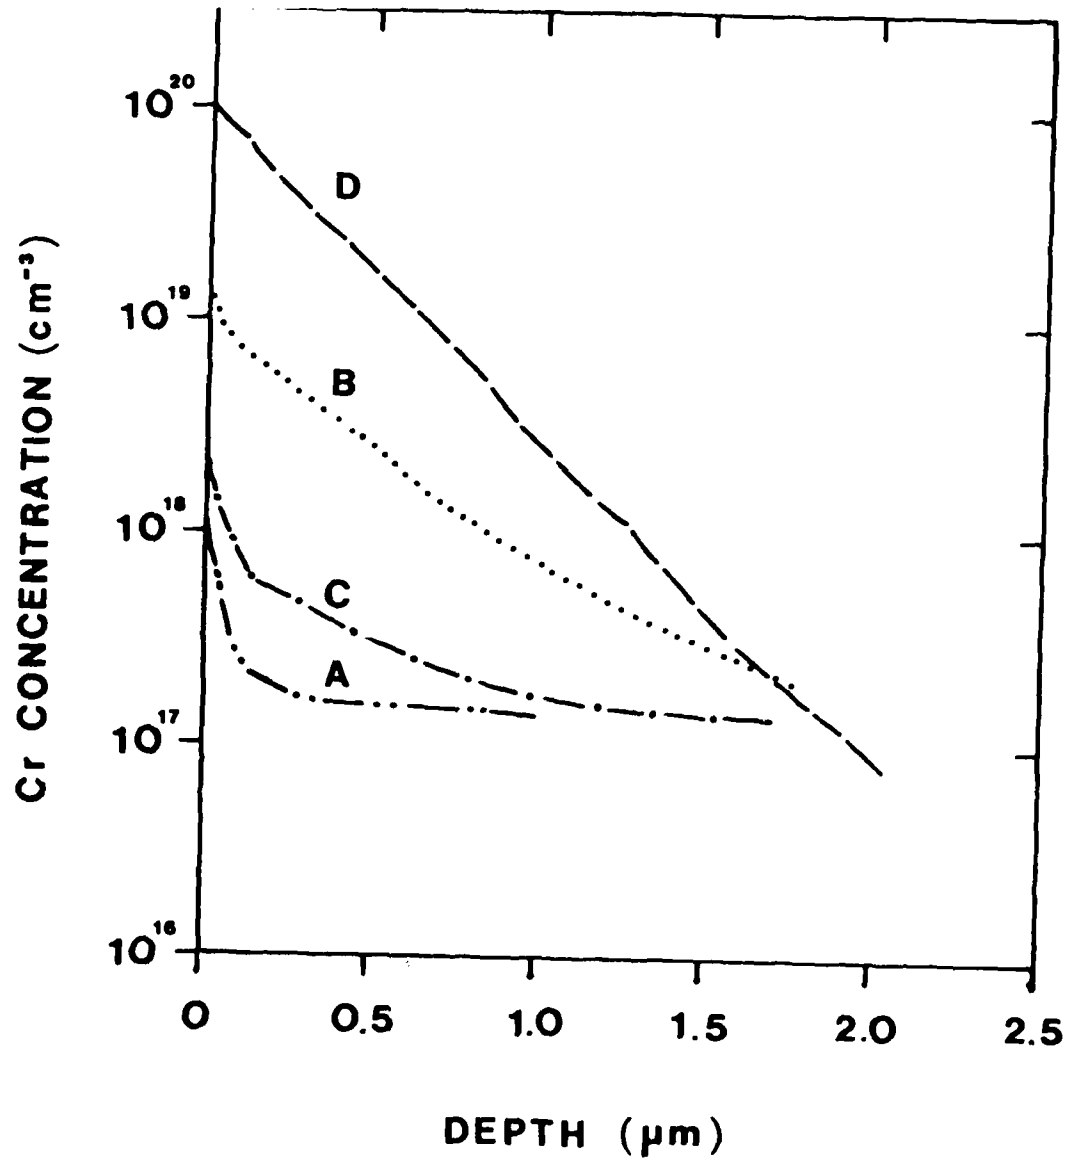


FIGURE 2. SIMS PROFILES OF BACK-SURFACE GETTERED Cr IN GaAs WAFERS; a) Control (no induced damage), Cr doped, annealed 800°C, 1 hr; b) Cr-doped, annealed 800°C, 0.5 hr; c) Cr-doped, annealed 800°C, 2.5 hr; d) Si-doped, Cr layer (front), annealed 800°C, 1 hr.

decreased. For anneal times  $>2.5$  hours, no additional reduction in Cr concentration is observed, and SIMS profiles are essentially identical to the results obtained at 2.5 hours.

For comparative purposes, we conducted a series of experiments on carefully selected Si-doped wafers shown by SIMS profiles to contain small concentrations of Cr. Layers of Cr were then deposited on the front surfaces of both control and back-surface-damaged samples and the specimens annealed at  $800^{\circ}\text{C}$ . Evidence of near-surface Cr gettering was observed at the back surfaces of control samples. In contrast, large accumulations of Cr were observed in back-surface-damaged samples annealed for comparable periods at  $800^{\circ}\text{C}$  (Figure 2), always exceeding the concentration for control samples. In agreement with the previous results, the gettered Cr was detected within a  $\approx 1.5\text{-}\mu\text{m}$  thick zone at the rear surface of the sample.

From the data obtained, we observe that the gettered Cr is positioned within a zone approximately equal to the depth of the distributed dislocation line structure at the back surface, as determined by TEM. The Cr concentration is also graded, approximately following the dislocation line gradient found in TEM measurements.<sup>7</sup> At short annealing times ( $\leq 1$  hr) the gettered Cr is relatively stable at the back surface, whereas for annealing periods  $> 1$  hr, the concentration of Cr is reduced as a function of increasing anneal duration. This reverse annealing or "degettering" effect can be directly correlated with the annealing of dislocation line structure reported in reference 7. As the damage is gradually annihilated with increasing anneal time, Cr is released and allowed to move back into the interior of the wafer. After 2.5 hours of annealing, the Cr concentration is relatively stable and no further modifications in SIMS profiles are observed. For anneal periods  $> 2.5$  hours, dislocation lines are also largely annihilated and only small concentrations of residual defects remain at the back surface.

The gettering of Cr from front surface layers is also directly related to the presence of dislocation line structure at the back side of the wafer. This anomalous diffusion of Cr may be related in part to the motion

of As vacancies released from the damaged region during annealing, or to the direct interaction between the strain field at the rear surface and Cr impurities at the front (or both). None of the experiments revealed the precipitation of Cr, in discrete zones or pinned sites along dislocation lines. The results suggest that the gettered Cr is present either in substitutional sites or in complexes not readily resolvable by TEM techniques.

To extend this study, we conducted a series of experiments in which a 2- $\mu\text{m}$  CVD  $\text{SiO}_2$  layer doped with As to a level of  $\approx 10^{20}$  atoms/cm<sup>3</sup> was used as an encapsulant at the rear surface of the back-surface-damaged wafer. It was found by TEM that the damage thermal stability time at temperatures in the range 700°C to 830°C could be increased by a factor of two, resulting in an apparent maximum of 4 hours available processing time at 800°C. As in the earlier investigations, annealing times in excess of the thermal stability time caused pronounced damage annihilation at the back surface.

To further supplement these data, the thick  $\text{SiO}_2$  caps were removed after annealing and SIMS profiles measured to ascertain the effect on Cr gettering. Using 30- $\mu\text{m}$  particles in the rotary abrasive damage procedure, we found that Cr was rapidly gettered after 0.5 to 1 hour of annealing at 800°C. For annealing times exceeding 2.5 hours, we found pronounced de-gettering, or reverse annealing of Cr, corresponding to the point at which damage annealing is pronounced at the back surface. In comparison to the results shown in Figure 2, however, reverse annealing is considerably altered and a longer period of time present before the mobile Cr is de-gettered and allowed to diffuse back into the interior of the GaAs wafer.

### 3. Back-Surface Gettering and Cr Outdiffusion in VPE GaAs Layers

Semi-insulating (Cr-doped) gallium arsenide has been widely used as a substrate material for the growth of epitaxial layers in fabricating microwave FET structures. To improve the performance of such devices, a buffer layer is commonly inserted between the substrate and active layer to reduce the outdiffusion of impurities into the active layer and to isolate the effects caused by defects propagating into the film at the substrate-epitaxial layer interface.<sup>10</sup> Recent experiments by Tuck et al.<sup>11</sup> using radiotracer techniques showed that Cr diffuses readily into VPE layers during epitaxial growth at substrate temperatures in the range 745°-750°C. Their data suggested that the rapid diffusion of Cr cannot be explained by simple substitutional diffusion and an interstitial diffusion mechanism must be invoked. Separate experiments using secondary ion mass spectrometry (SIMS) and transmission electron microscopy/diffraction (TEM/TED) on Ne ion-implanted or mechanically-damaged back surfaces of GaAs wafers<sup>8,12</sup> have also shown rapid motion and subsequent gettering of Cr at 750°-800°C for anneal times in the range 0.5-1 hour, thereby lending additional support for a non-substitutional diffusion mechanism.

The concentration of point defects and dislocation lines at the substrate-epilayer interface will exercise an important influence on the outdiffusion of Cr and other impurities into the epitaxial layer. Improvements in the quality and microstructural defect content of epitaxial GaAs layers have been previously noted when back-surface-damaged, pre-gettered substrates were used.<sup>13,14</sup> However, to our knowledge, there have been no reports of the effect of (substrate) damage pre-gettering on the outdiffusion of Cr into epitaxial layers during growth. In the next sections, correlated data from TEM and SIMS measurements are presented which show the influence of substrate gettering on the interfacial defect density and distribution of Cr in VPE layers during growth and subsequent annealing.

#### 3.1 Experimental Procedure

The semi-insulating GaAs wafers used in this study were obtained from two independent suppliers and were Cr-doped to achieve resistivities

greater than  $10^7$  ohm. cm. The wafers were typically oriented  $3^\circ$  off the (100) toward the (110) and were polished on one side.

After cleaning, the polished front surfaces were coated with 2000Å of  $\text{SiO}_2$  deposited in a commercial pyrolytic decomposition reactor at  $400^\circ\text{C}$ . The oxide film served as a scratch protection layer during back surface damage operations. A rotary abrasive unit was used to create macroscopic, concentric damage grooves ( $\leq 30 \mu\text{m}$ ) at the back surface of the wafer. After completion of the damage process, the  $\text{SiO}_2$  layer was removed and a 1000Å thick  $\text{Si}_3\text{N}_4$  encapsulant formed on the front surface at  $200^\circ\text{C}$  by plasma deposition. Anneals were done in flowing  $\text{H}_2$  at temperatures in the range  $750^\circ\text{C}$ - $900^\circ\text{C}$ .

Following the anneal, the  $\text{Si}_3\text{N}_4$  film was removed and the wafers loaded into a vapor phase epitaxial reactor and heated to the deposition temperature of  $720^\circ\text{C}$ . After a brief vapor etch, undoped epitaxial "buffer" layers were grown on both gettered and control wafers in the same run. The GaAs buffer layers were grown using a standard hydride ( $\text{AsH}_3 + \text{HCl} + \text{Ga}$ ) reactor typically utilized for growing epitaxial material (active/buffer) for GaAs MESFET requirements.

Following epitaxial growth, samples were prepared for TEM/TED analysis by conventional jet-thinning techniques and examined in the microscope using bright- and dark-field electron microscopy. SIMS profiling was done in a Cameca IMS-3f ion microanalyzer. To obtain maximum Cr sensitivity,  $\text{O}_2^+$  bombardment was combined with positive secondary ion mass spectrometry. The Cr concentration levels were determined using standards prepared by ion implanting Cr into both epitaxial layers and semi-insulating GaAs substrates.

### 3.2 Results

TEM examination of back-surface-damaged samples showed that the rotary abrasive technique produces a heavily-forested, laterally-continuous array of dislocations extending to a depth of  $\approx 1.5 \mu\text{m}$  below the depth of damage grooves at the back surface. Fig. 3 shows a plot of the measured dislocation



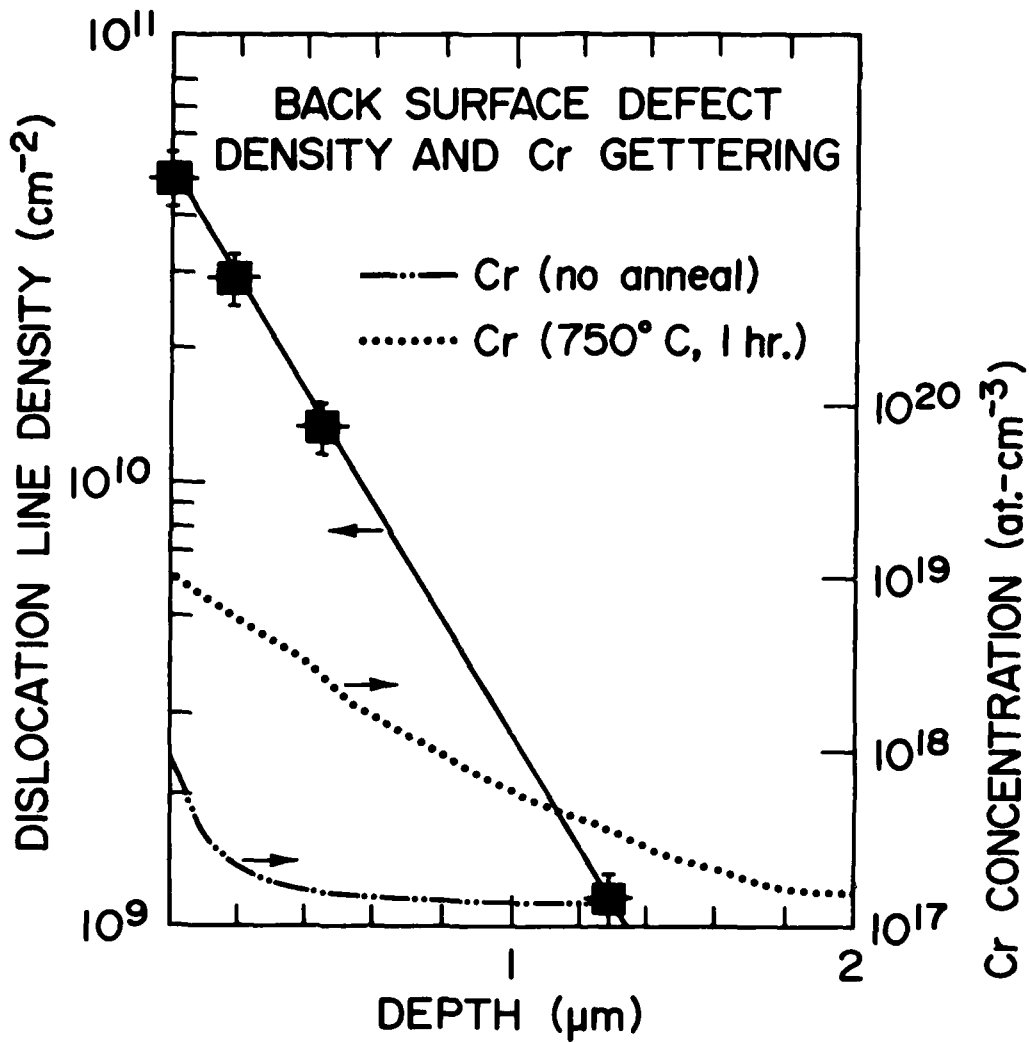


FIGURE 3. DEFECT DENSITY AND Cr CONCENTRATION PROFILES OF BACK-SURFACE DAMAGED ANNEALED GaAs SUBSTRATES.


line density as a function of depth from the back surface. Also shown for reference is a SIMS profile of the Cr concentration at the back surface before and after annealing at 750°C for 1 hour. No significant dislocation line structure was observed in any sample at depths >1.5  $\mu\text{m}$ . Correspondingly, the gettered Cr is concentrated within a region approximately equal to the width of the damage region. TEM examinations of the annealed samples show no evidence of precipitation along dislocation lines or in discrete segregation zones, suggesting that the Cr is present either in the form of complexes or regions not readily detectable by conventional TEM techniques.

To further investigate the effect of gettering at the front surface, we annealed for 1 hour at 750°C both control (no back-surface damage) and back-surface-damaged samples. A low-temperature (200°C) plasma-deposited  $\text{Si}_3\text{N}_4$  layer (1000Å thick) was used as the encapsulant. The  $\text{Si}_3\text{N}_4$  encapsulants were removed and samples immersed in a  $\text{H}_2\text{SO}_4:\text{H}_2\text{O}_2:\text{CH}_3\text{COOH}(3:1:1)$  solution for 2 minutes.


Fig. 4 shows optical micrographs of the front surfaces of annealed control (Fig. 4a) and gettered (Fig. 4b) substrates after immersion in the etch solution. The number of etch figures is considerably reduced in the gettered sample while the control samples consistently showed a density  $>2 \times 10^4/\text{cm}^2$ . These experiments were then repeated for a number of samples with essentially identical results.

Correlated TEM examinations of the front surfaces also showed a reduction in substrate dislocation line density after gettering. To isolate any possible capping effect, unannealed and annealed control (capped) samples, prepared under similar conditions were examined and no appreciable reduction in defect density was observed. Examination of VPE layers grown on gettered and ungettered substrates showed that the defect density in layers grown on gettered substrates was drastically reduced, essentially in agreement with the results of Schwuttke and Yang<sup>13</sup> on epitaxial GaAs layers grown on gettered substrates which were mechanically damaged at the back surface by impact sound stressing.

To determine the influence of gettering on Cr redistribution, SIMS

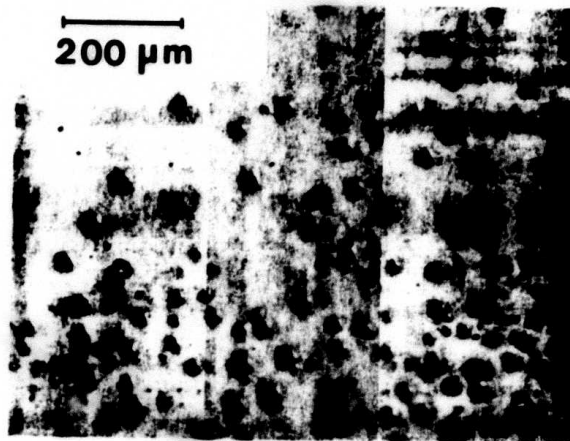

**(a)**

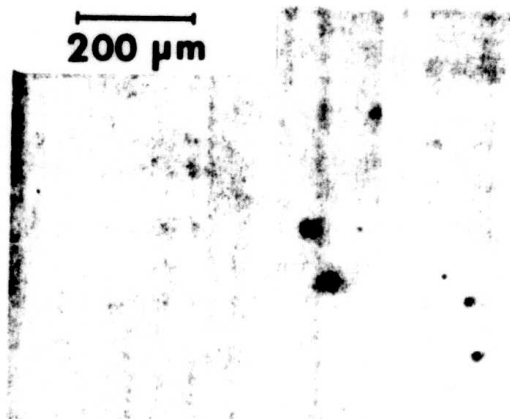

**(b)**

FIGURE 4. OPTICAL MICROGRAPHS OF ETCH FIGURES OF ANNEALED  
SAMPLES: a) Control; b) Gettered.

measurements were made to obtain Cr concentration profiles on the substrate and epitaxial layers. Fig. 5 shows SIMS profiles of the  $^{52}\text{Cr}$  concentration in VPE layers on gettered and ungettered substrates after deposition and annealing. Fig. 5a) shows that Cr has outdiffused rapidly during deposition in layers grown on both gettered and control (ungettered) substrates. However, the level of outdiffused Cr is significantly higher for the epitaxial layer on a control substrate. In all samples examined, the level of Cr was found to be reduced in VPE layers grown on pre-gettered substrates.

Figure 5b) shows the  $^{52}\text{Cr}$  distributions in post-deposition annealed ( $800^{\circ}\text{C}$ , 30 min.) VPE layers grown on gettered and ungettered ( $\text{Si}_3\text{N}_4$  capped) substrates. The data suggest that the total Cr content in the VPE layer grown on the ungettered substrate is considerably greater than the Cr content in the epilayer grown on the pre-gettered substrate. Comparing Figs. 5a) and 5b), it can be seen that the outdiffusion of Cr is suppressed in the pre-gettered sample whereas the Cr in the control substrate moves rapidly through the layer to the surface of the sample. The apparent near-surface pileup of Cr in both samples is thought to be a strain-induced effect caused by thermal mismatch between the encapsulant and the GaAs epilayer.<sup>15</sup>

Annealing at temperatures  $\geq 850^{\circ}\text{C}$  produces significant Cr diffusion into VPE layers with no noticeable difference between profiles obtained on control or pre-gettered samples. TEM examinations of gettered samples annealed at higher temperatures also show that the back-surface damage is progressively annihilated as a function of increasing temperature and anneal duration. It can then be speculated that the removal of back-surface damage and strain gradients caused by the presence of a graded dislocation line density (Fig.3) will correspondingly remove any apparent suppression of Cr outdiffusion from the substrate into the epitaxial layer.

From the data obtained, we can conclude that back-surface-damage gettering reduces the concentration of microstructural defects at the substrate surface and within the epitaxial layer. Since both point defects and line defects will contribute to enhanced diffusion of an impurity, the outdiffusion of Cr will be reduced during growth of VPE layers on pre-gettered


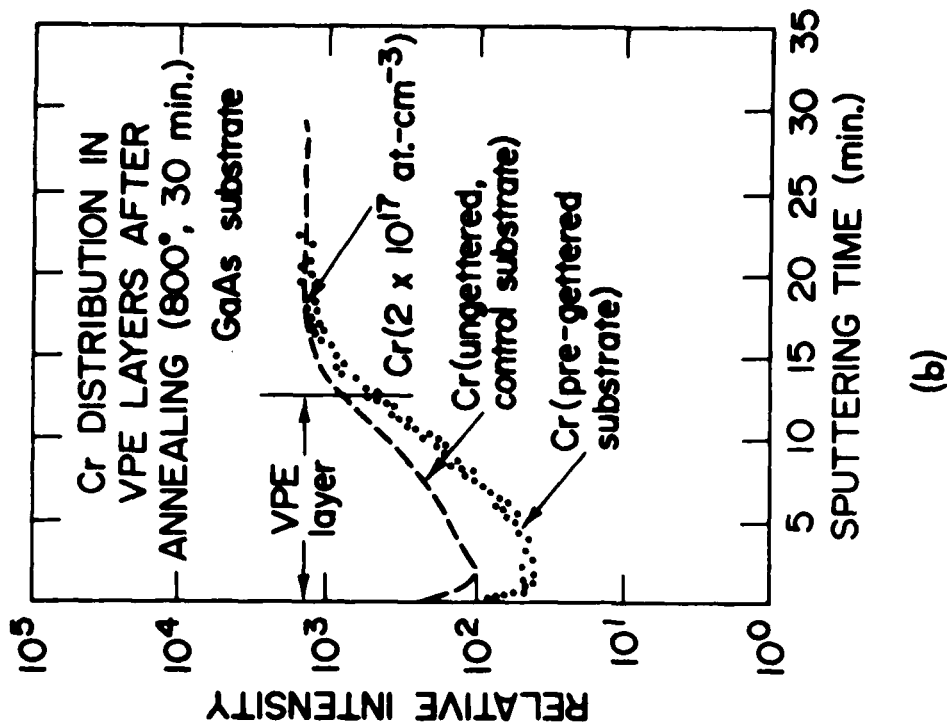


FIGURE 5. SIMS PROFILES OF Cr CONCENTRATION IN SUBSTRATES AND VPE LAYERS AFTER DEPOSITION AND ANNEALING: a) After deposition; b) 800°C post deposition anneal ( $t_{VPE}=1.7\mu m$ ).

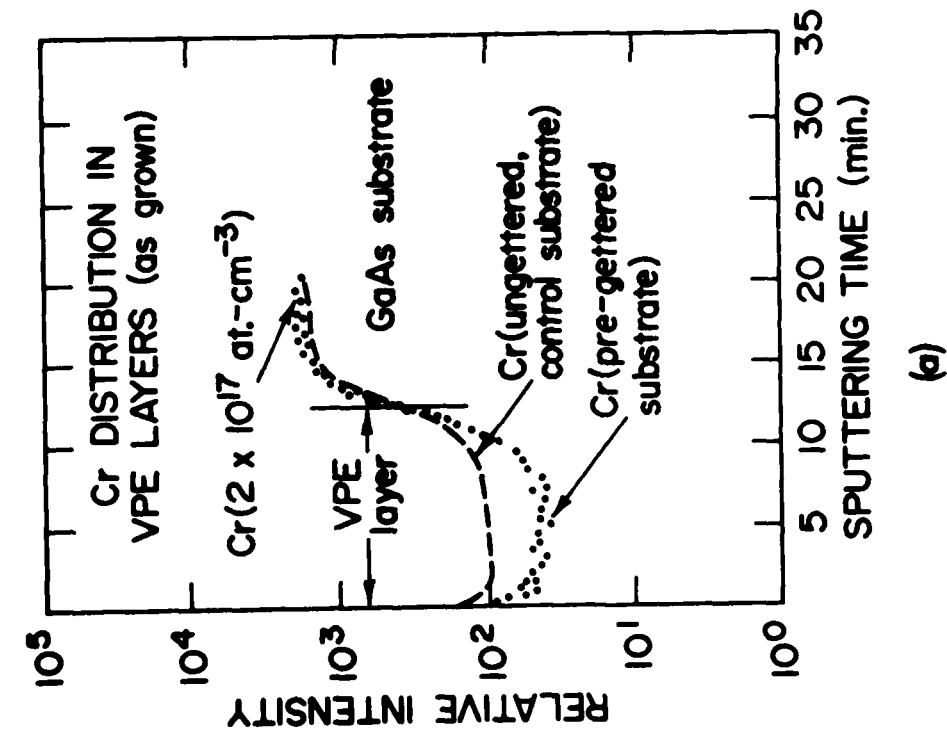

substrates. During post-deposition annealing, the presence of a strain field gradient produced by the dislocation line density at the back surface will partially suppress the outdiffusion of Cr and will be effective until back-surface damage is annihilated at high temperature anneals.

#### 4. ALLOYING OF Au LAYERS AND REDISTRIBUTION OF Cr IN GaAs

The increasing utilization of GaAs as a material for fabricating microwave field effect transistors (FET), Gunn-effect diodes, and IMPATT diodes has, over the past 15 years, prompted a number of investigations on the annealing behavior of contact structures. In particular, the alloying characteristics of Au-Ge and Au-Ge-Ni structures on n-type GaAs have been widely reported,<sup>16-24</sup> but the problems of thermal aging and the processes which create high resistivity layers near the surface have yet to be satisfactorily resolved.<sup>25-27</sup> The deterioration of contact regions has in the past been ascribed to the indirect effects of strain-induced damage at the interface,<sup>27,28</sup> or to compensation of the Ge dopant by acceptors associated with As vacancies.<sup>30</sup>

Recent studies on VPE layers grown on Cr-doped (semi-insulating) GaAs substrates have shown that Cr out-diffuses readily into the epitaxial layers during deposition and annealing.<sup>11,29</sup> Another investigation has shown that Cr is rapidly gettered into the region of residual damage and interface of Se-implanted (capped) GaAs substrates, suggesting a possible correlation between Cr redistribution and the development of high resistivity layers at the surface after annealing.<sup>30</sup>

To our knowledge, there have been no reported studies of the effect of contact alloying on the redistribution of Cr at annealing temperatures in the range 350-370°C. In this section, data from transmission electron microscopy (TEM) and secondary ion mass spectrometry (SIMS) measurements are presented which show the development of damage structure and redistribution of Cr in n-type LPE layers and semi-insulating substrates after alloying thin Au films at 350°C for varying anneal times.

##### 4.1 Experimental

Semi-insulating GaAs wafers used in this study were of (100) orientation and Cr doped to obtain resistivities  $>10^7 \Omega\text{cm}$ . The LPE layers (0.5  $\mu\text{m}$  thick) on semi-insulating substrates were Sn doped to levels of  $1 \times 10^{17}$  atoms  $\text{cm}^{-3}$ . Gold films were vapor deposited at room temperature on

precleaned samples at initial vacuum levels  $<10^{-8}$  Torr. Annealing was done at  $350^{\circ}\text{C}$  in a flowing  $\text{H}_2$  environment. In all cases, samples were rapidly removed from the furnace after annealing and placed on a heat sink to achieve fast cooling rates.

After the removal of Au layers, specimens were prepared for TEM analysis using standard jet thinning techniques and examined in the microscope. SIMS profiling was performed with a Cameca IMS-3f ion microanalyzer. The SIMS depth profiles used  $\text{O}_2^+$  primary ion bombardment and positive secondary ion spectroscopy. The  $^{71}\text{Ga}_2^+$  molecular ion (designated  $^{142}\text{Ga}$  in the figures) was used to establish the Ga-concentration profile since the singly charged  $\text{Ga}^+$ -ion yield was too intense to measure with the electron multiplier. The Cr atomic concentration was calibrated using a  $^{52}\text{Cr}^+$ -ion implant into GaAs.

#### 4.2 Results

To examine initial defect content in substrate and LPE layers, we immersed samples in a  $\text{H}_2\text{SO}_4:\text{H}_2\text{O}_2:\text{CH}_3\text{COOH}(3:1:1)$  solution for 2 min. Optical microscopy examination showed surface defect densities  $\approx 2 \times 10^4 \text{ cm}^{-2}$  in all samples tested. After deposition of Au layers, we removed the films and again etched substrates and LPE layers. The results showed no appreciable change in defect density, indicating that no dramatic increases in defect density are produced in these experiments by Au deposition alone. Since etching experiments cannot adequately be used to reveal individual dislocation lines on alloyed surfaces, we used TEM analysis on both alloyed and control samples to obtain additional information on microstructure induced as a result of the alloying process. After Au deposition and subsequent annealing, we found a complex array of dislocations in the form of nests and tangles (Fig. 6). In contrast, we found no evidence of such arrays in control substrates or unannealed Au/GaAs structures. Annealing for periods up to 10 min. at  $350^{\circ}\text{C}$  appeared to increase the amount of damage in direct proportion to the annealing time, essentially in agreement with earlier results of Gyulai et al.<sup>24</sup> obtained by back scattering. Annealing of 4000Å-thick Au films for comparable periods

produced a significant increase in dislocation density, suggesting that the defect density induced by alloying is directly proportional to the initial film thickness.

Examination of samples with deposited Au films of 1000 $\text{\AA}$  thickness on LPE layers also showed the same pattern of complex dislocation networks as shown in Fig. 6 after annealing at 350 $^{\circ}\text{C}$  for 1 min. In like manner, additional alloying time increased the amount of damage present within the epitaxial layer.

Recent studies of Cr gettering in GaAs<sup>12,29,30</sup> have shown that Cr can exceed solid solubility in regions containing large amounts of crystalline damage without inducing additional microstructural damage in the lattice. From these results and earlier investigations of damage induced in GaAs as a result of Au alloying, we can conclude that the observed damage in these experiments is associated with Au diffusing into the GaAs during alloying and not correlated with any Cr redistribution.

To obtain the in-depth data on the distribution of Cr within the substrate and Au film, we used SIMS profiling. In Fig. 7 we show chemical profiles of an Au/GaAs structure after deposition of a 1000 $\text{\AA}$ -thick Au layer and annealing at 350 $^{\circ}\text{C}$  for periods of 1, 3, and 10 min. In Fig. 7a), we observe that after 1 min. of annealing, the Au has diffused into the GaAs substrate, accompanied by outdiffusion of both Ga and As through the Au layer to accumulate on the surface of the film. These results are in general agreement with earlier studies using Auger electron spectroscopy profiling.<sup>21,31,32</sup> Of particular importance is the near-surface pileup of Cr and subsequent outdiffusion from the substrate onto the surface of the Au film. In all samples examined we observed similar pileups of Cr within the substrates near the interfacial region. For comparison we also obtained SIMS profiles on unannealed Au/GaAs structures and found no evidence of Cr interfacial pileup or outdiffusion after deposition. After 3 min. of annealing [Fig. 7b)], the concentration of Cr is reduced in the near-surface region and outdiffusion into the Au film is further increased. Ten minutes of annealing produces substantial outdiffusion of Ga [Fig. 7c)] and an apparent annihilation of the sharply defined "knee" in the Cr



FIGURE 6. TRANSMISSION ELECTRON MICROGRAPH OF GaAs UNDER (1000 Å thick) Au CONTACT LAYER AFTER ANNEALING AT 350°C FOR 1 MINUTE.

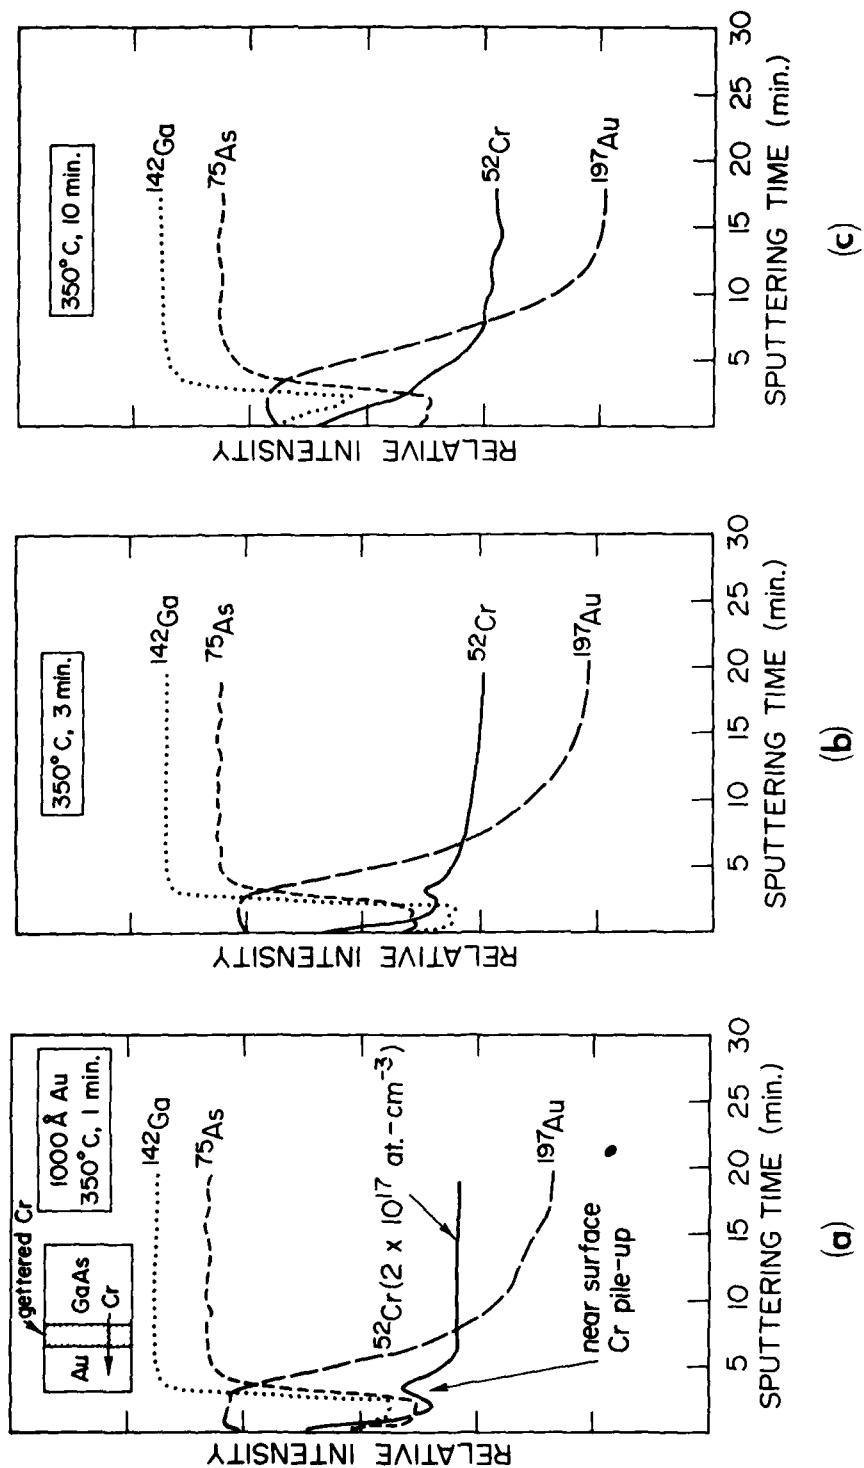


FIGURE 7. SIMS PROFILES OF  $(1000\text{\AA})$  Au/GaAs STRUCTURE AFTER ANNEALING AT  $350^\circ\text{C}$ ; a)  $t_A=1$  min; b)  $t_A=3$  min; c)  $t_A=10$  min.

distribution profile observed in Fig. 7a).

Similar experiments conducted on Sn-doped LPE layers on semi-insulating substrates showed that Cr outdiffused readily during deposition, approaching a level of  $(1-2) \times 10^{16}$  atoms  $\text{cm}^{-3}$  throughout the epitaxial layer. After deposition of a 1000Å-thick Au film on the LPE layer and annealing at 350°C for variable times, we observed essentially the same redistribution of Cr at the near surface region and within the Au film as shown in Fig. 7.

To further investigate the effect of alloying on the redistribution of Cr, we increased the thickness of Au films on semi-insulating substrates to 4000Å annealed at 350°C for periods of 1 to 10 min. Fig. 8 shows the resulting SIMS profiles of the Au/GaAs structure after anneals of 1 to 10 min. Qualitatively, we observe a similar pattern of Cr outdiffusion and gettering within the near-surface region, producing a sharply defined "knee" in the Cr-concentration profile after a 1-min anneal [Fig. 8a)].

From the data shown, we can conclude that alloying of Au films on semi-insulating GaAs substrates or LPE layers on (semi-insulating) GaAs produces a region of damage and strain within the GaAs lattice. The concentration of damage increases as a function of initial film thickness for comparable anneal durations at 350°C. This induced damage can serve as an effective gettering region for Cr (and potentially other impurities).

In all cases, Cr outdiffuses readily into the Au layer at 350°C and accumulates at the surface of the film. The data suggest that the degradation or aging of Au-Ge or Au-Ge-Ni contacts on n-type epitaxial layers grown on semi-insulating (Cr-doped) GaAs wafers may be related both to the generation of dislocation lines and the outdiffusion and gettering of Cr at the contact region. Additional studies are currently being done to evaluate the effect of Cr redistribution in near-surface regions on the electrical properties of contact structures.


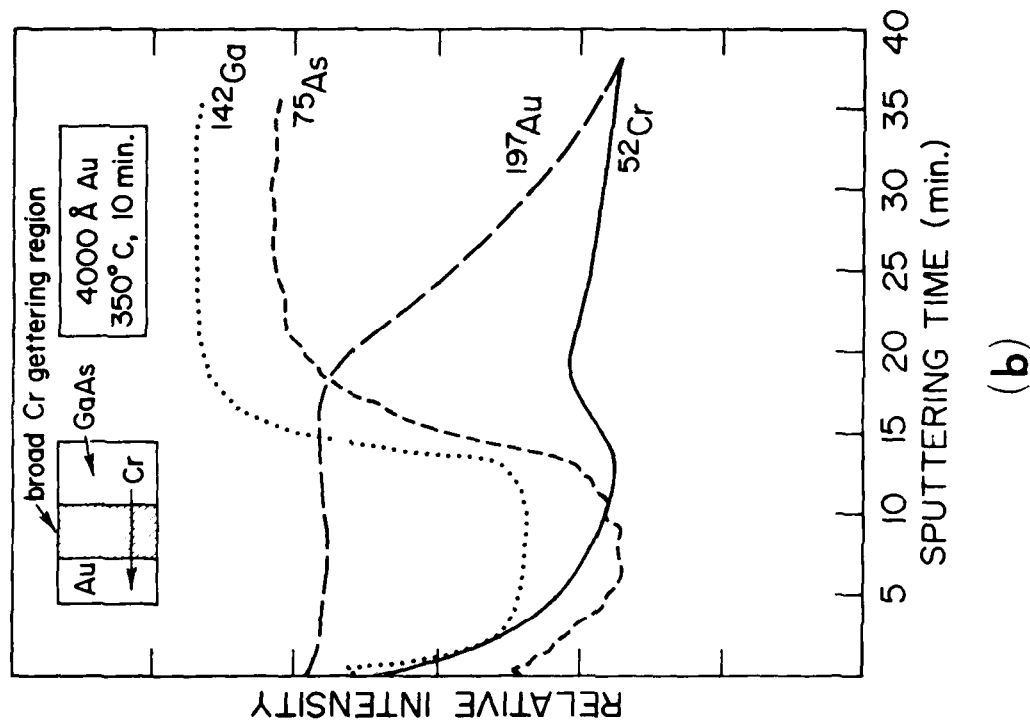


FIGURE 8. SIMS PROFILES OF (4000Å) Au/GaAs STRUCTURE AFTER ANNEALING AT 350°C; a)  $t_A = 1$  min; b)  $t_A = 10$  min.

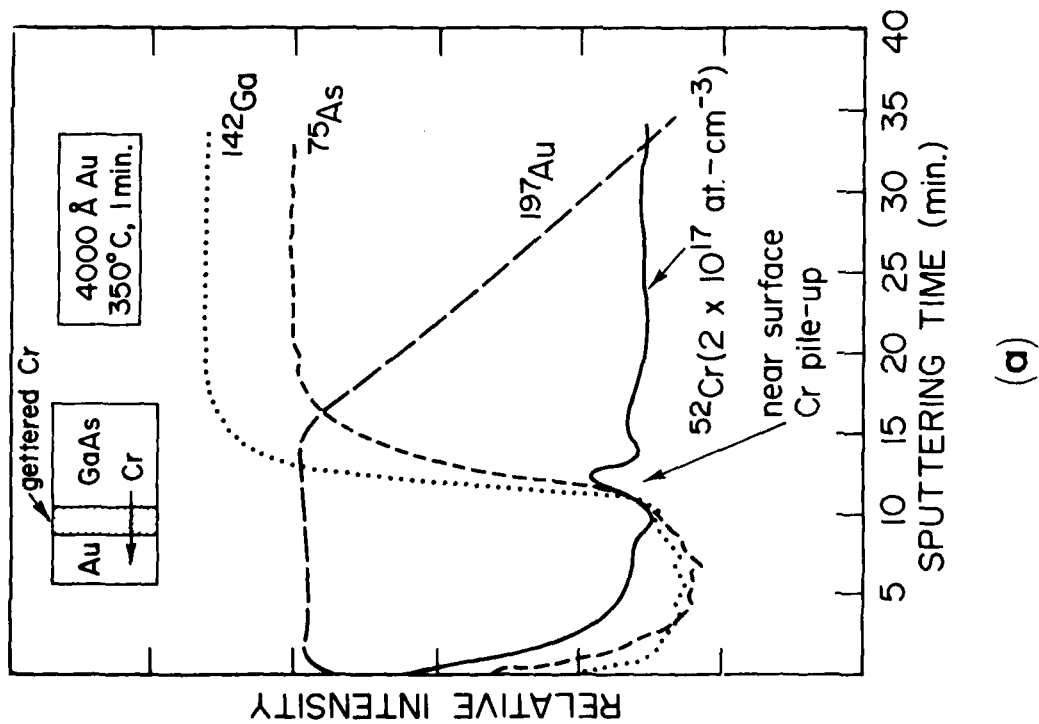

## 5. PERFORMANCE OF FET STRUCTURES FABRICATED IN VPE LAYERS ON PRE-GETTERED SUBSTRATES

In the previous section, it was shown that significantly improved VPE layers are obtained when the epitaxial structures are grown on pre-gettered SI-GaAs substrates. In addition to reducing the substrate defect density at the front surface and within the interfacial region, back-surface-defect pre-gettering techniques were found to significantly reduce the outdiffusion and redistribution of Cr during deposition and subsequent annealing. To ascertain the effectiveness of these techniques for improving the yield and performance of FET devices, it was necessary to evaluate the interface mobility, capacitance and actual performance of FETs fabricated in VPE layers on pre-gettered substrates.

Samples used in this experiment were selected at random for wafer lots with no pre-screening tests performed, thereby assuring that the wafers were representative of as-received material from the supplier. One half of selected wafers was used for control specimens and the other half used for gettering in separate tests. In several sets of experiments, the entire wafer was used for gettering and VPE layer growth. Pre-gettering was accomplished using techniques described in the previous sections and earlier reports. A getter pre-anneal was done at 800°C for 30 minutes on back-surface-damaged samples with a plasma-deposited (low-oxygen-content)  $\text{Si}_3\text{N}_4$  cap on the front surface. After annealing and removing the  $\text{Si}_3\text{N}_4$  cap, VPE layers were grown on the substrates in a standard hydride reactor at Avantek, Inc.

Figures 9 and 10 show representative data obtained at Avantek on VPE layers grown on control (not gettered) and pre-gettered Cr-doped substrates. It is apparent that the mobility at the interface on the pre-gettered sample is significantly higher than that observed on the control sample. Tables 1 and 2 present representative comparative data obtained at 6 GHz, 12 GHz, and 18 GHz on FET devices fabricated on control and pre-gettered wafers. The data sheets shown illustrate that FETs in epi-layers on control (non-gettered) substrates. Of particular significance is the reduction (0.7 dB) in noise figure at 18 GHz.

FIGURE 9. PROFILE-VPE/GaAs (CONTROL) SAMPLE.


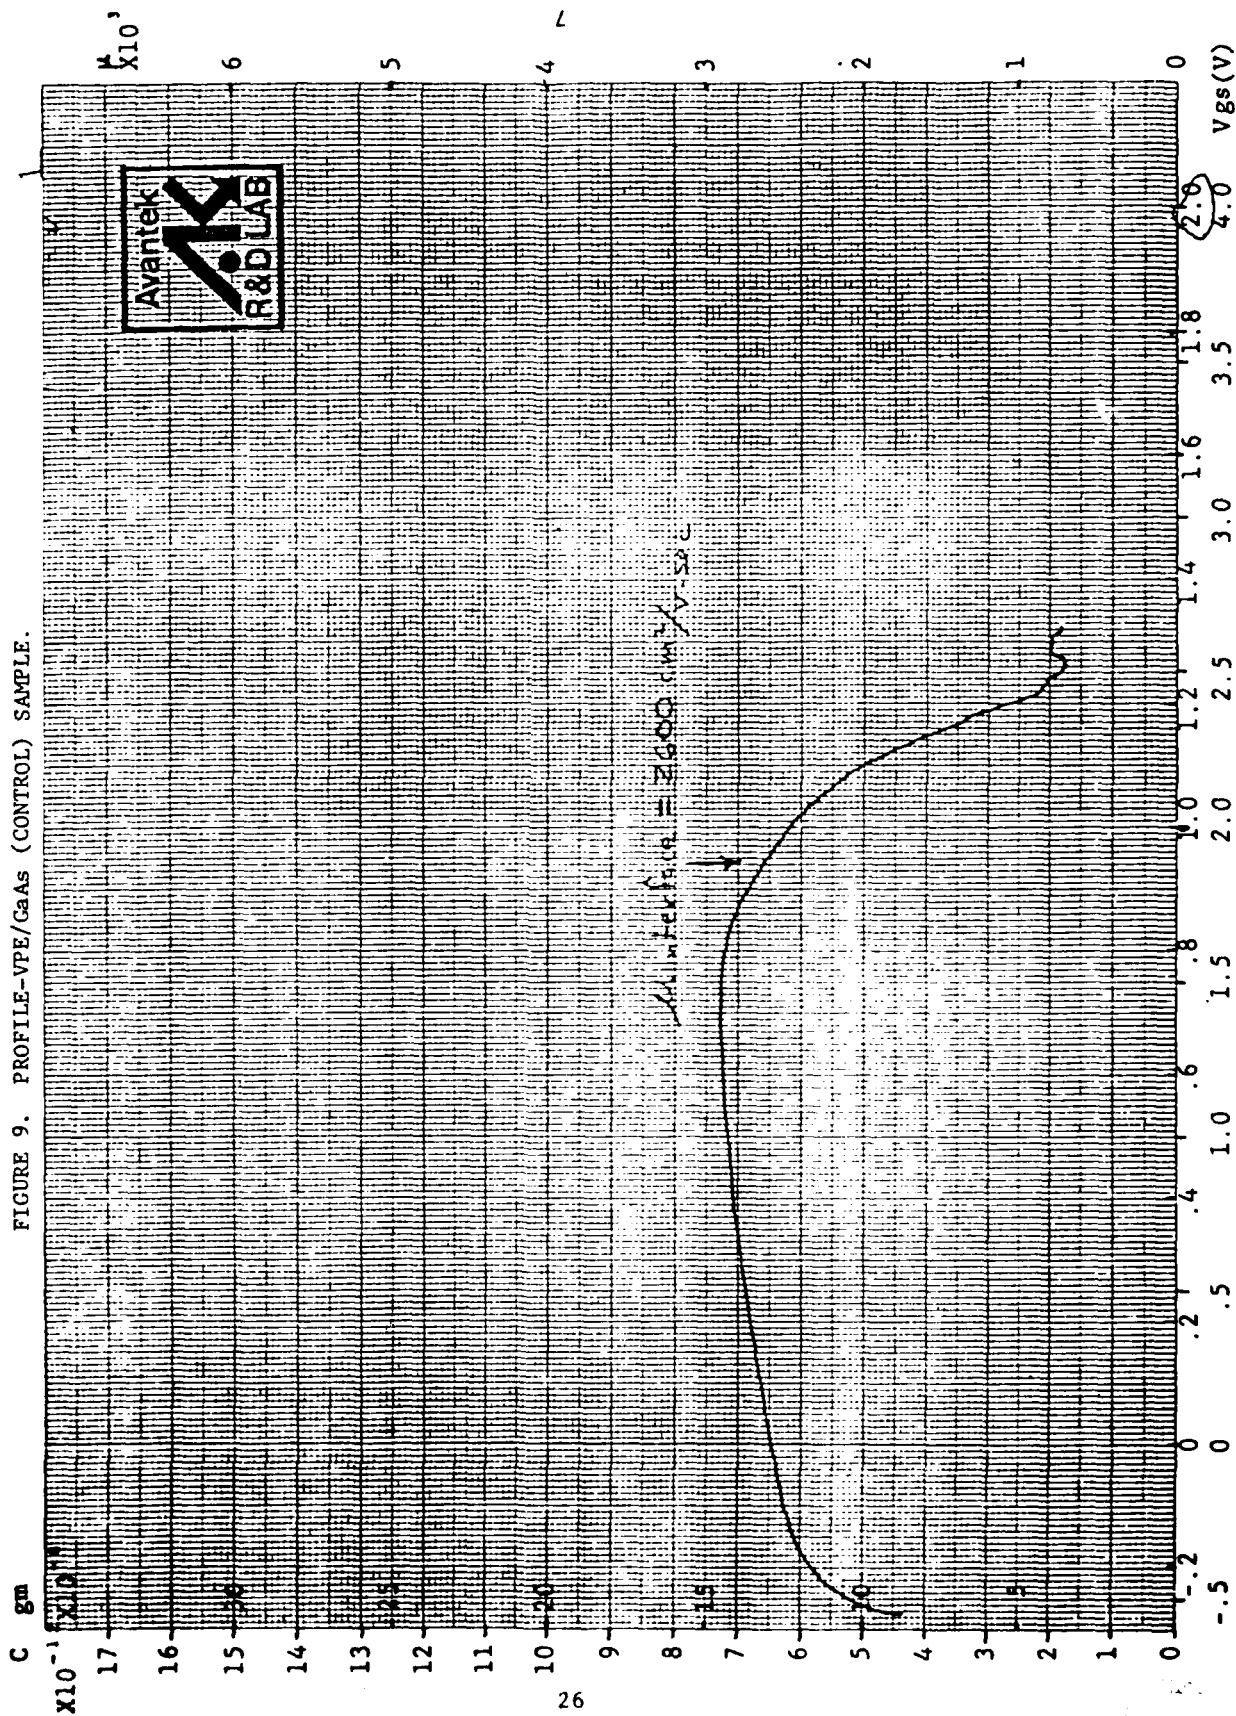


FIGURE 10. PROFILE-VPE/GaAs (PRE-GETTERED) SAMPLE.

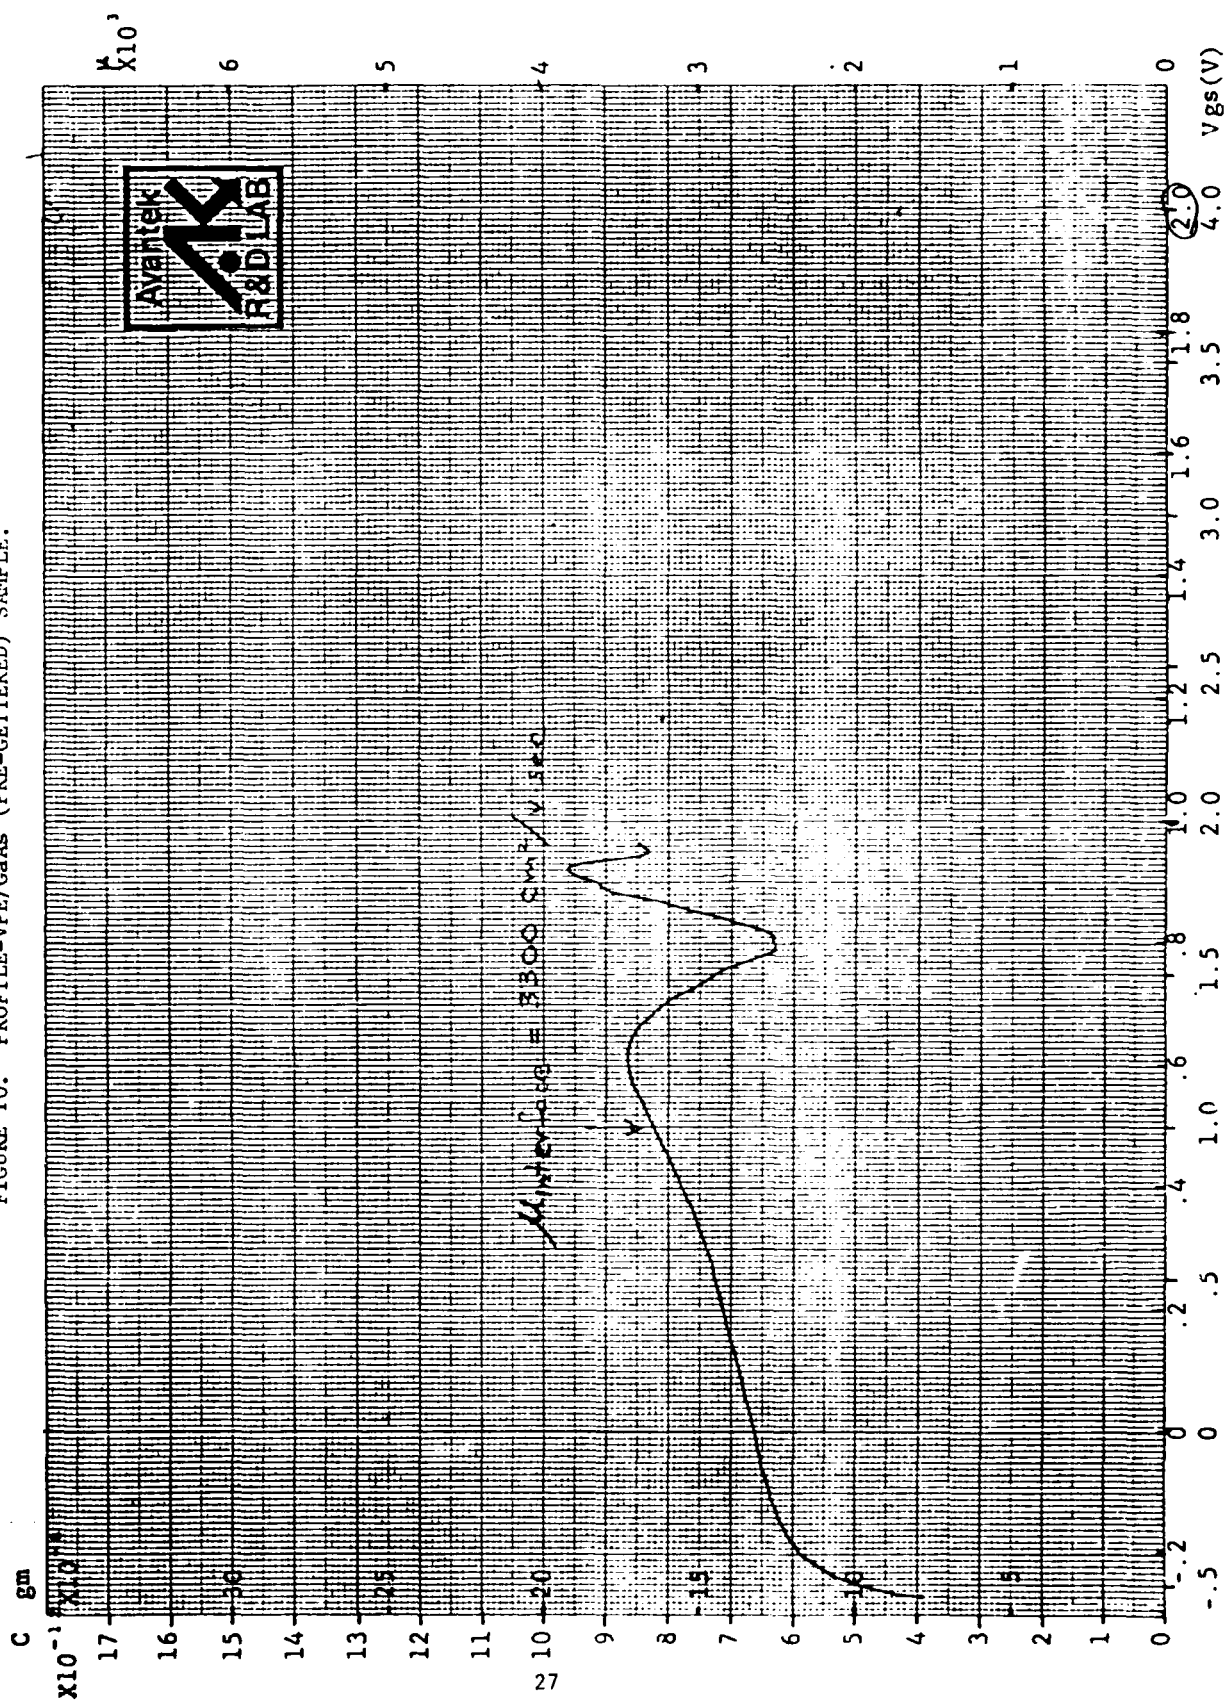

Test		1	2	3	4	5	6	7	8	9	10
DC	$I_{dss}$ at $V_{ds}$ <u>3</u> V	45	46	31	29	30					
	$R_{do}$	16	16	20	21	20					
	$G_{mo}$ at $V_{ds}$ _____, $I_{ds}$ _____										
	$G_{mo}$ at $V_{ds} = 3V$ , $I_{dss}$	50	49	45	44	45					
	$V_p$ at $V_{ds} = 3V$ , $I_{ds} = 1$ mA	1.0	1.1	.78	.74	.78					
	$BV_{gs}$ at $I_{gs} = 1$ (10 $\mu A$ )	7.2	7.5	10	11	11					
RF	6 GHz, $F_2 = 2.65$ dB, DATE 6 / 14 / 79	$V_{ds}/I_{ds}$ (V/mA)	4/8	4/7	4/7	4/8	4/7				
		$F_{12}$ (dB)	1.7	1.6	1.65	2.0	1.75				
		GA (dB)	2.2	12.3	12.2	12.1	12.4				
		$F_0$ (dB)	1.55	1.45	1.5	1.86	1.61				
		$F_{\infty}$ (dB)	1.63	1.53	1.58	1.95	1.69				
	12 GHz, $F_2 =$ _____ dB, DATE / /	$V_{ds}/I_{ds}$ (V/mA)	3.5/10	4.4/7	6/5	4/6	3.5/5				
		$F_{12}$ (dB)	2.8	2.65	2.5	3	3				
		GA (dB)	9.8	9.6	8.3	8.6	8.7				
		$F_0$ (dB)	2.31	2.11	2.09	2.37	2.31				
		$F_{\infty}$ (dB)	2.51	2.31	2.37	2.65	2.66				
	18 GHz, $F_2 =$ _____ dB, DATE / /	$V_{ds}/I_{ds}$ (V/mA)	12/12.5	1.1/9	10/8	1.7/6.5	10/7				
		$F_{12}$ (dB)	1.5	3.9	4.6	4.3	4.35				
		GA (dB)	7	7.8	6.8	6.5	6.7				
		$F_0$ (dB)	3.21	2.68	3.28	2.74	2.90				
		$F_{\infty}$ (dB)	3.74	3.26	3.25	3.29	3.44				

Table 1. Device Data - Control (Ungettered) Substrate

Test		1	2	3	4	5	6	7	8	9	10
DC	$I_{dss}$ at $V_{ds} = 3$ V	34	34	34	7	7.5					
	$R_{do}$	21	20	21	54	54					
	$G_{mo}$ at $V_{ds} =$ , $I_{ds}$										
	$G_{mo}$ at $V_{ds} = 3V$ , $I_{dss}$	43	42	43	25	26					
	$V_p$ at $V_{ds} = 3V$ , $I_{ds} = 1$ mA	1.0	1.0	1.0	.36	.36					
	$BV_{gs}$ at $I_{gs} = 1/10$ $\mu A$	4.4	12	12	18	18					
RF	6 GHz, $F_2 = 2.65$ dB, DATE 6 / 14 / 79	$V_{ds}/I_{ds}$ (V/mA)	3/7	2.5/8	2.5/8	2/6	2/6				
		$F_{12}$ (dB)	1.55	1.6	1.6	1.8	1.8				
		GA (dB)	12.0	12.1	12.4	12.0	11.5				
		$F_0$ (dB)	1.39	1.44	1.45	1.65	1.63				
		$F_{\infty}$ (dB)	1.46	1.52	1.53	1.74	1.73				
	12 GHz, $F_2 =$ dB, DATE / /	$V_{ds}/I_{ds}$ (V/mA)	2.5/9	3/8	3/7	2.5/7					
		$F_{12}$ (dB)	2.5	2.6	2.55	3.4					
		GA (dB)	10.1	9.6	9.0	8.8					
		$F_0$ (dB)	2.51	2.06	2.03	2.56					
		$F_{\infty}$ (dB)	2.18	2.25	2.21	3.16					
	18 GHz, $F_2 =$ dB, DATE / /	$V_{ds}/I_{ds}$ (V/mA)	6/9	6.5/6	6.5/5.5	8.3/5.5					
		$F_{12}$ (dB)	3.2	3.15	4.10	4.70					
		GA (dB)	7.7	6.3	7.3	5.45					
		$F_0$ (dB)	2.51	2.13	2.57	2.83					
		$F_{\infty}$ (dB)	2.89	2.62	3.6	3.57					

Table 2. Device Data - Pre-gettered Substrate

The results show that pre-gettering of GaAs substrates yields the following:

- o Reduction or annihilation of defects within the substrate and epitaxial layer.
- o Reduction of Cr outdiffusion from the substrate during deposition and subsequent annealing.
- o Higher interface mobilities.
- o Lower NF at high frequencies.
- o Lower input capacitance.
- o Higher apparent device yields per wafer.

Tests are continuing on a number of wafers to determine the statistical improvement in device yield and performance.

## 6. CONCLUSIONS AND FUTURE EXPERIMENTS

In this period of the research program, we have shown that Cr is readily gettered by back-surface mechanically-induced damage at temperatures in the range 730°C to 850°C. It has been demonstrated that reverse gettering or "de-gettering" of Cr occurs after extended annealing, corresponding to the time at which dislocation structure at the rear surface of the wafer is gradually annihilated. To extend the useful annealing or gettering time, a thick 2- $\mu\text{m}$   $\text{SiO}_2$  layer, doped with As to a level of  $10^{20}$  atoms/cm<sup>3</sup>, was deposited on the back surface prior to annealing to retard the annihilation of damage structure, producing an increase in the damage stability period at gettered Cr retention time.

To investigate the applicability of back-surface-damage techniques for improving the quality of epitaxial layers grown on SI-GaAs substrates, VPE layers were prepared (in a standard hydride reactor) on both control (ungettered) and pre-gettered Cr-doped substrates. It was found that the substrate and epi-substrate interfacial defect density was significantly reduced at the front surface. In addition, Cr outdiffusion from the substrate into the VPE layer was substantially reduced during deposition and subsequent annealing.

Investigations of Au contact layers on substrates and LPE layers have shown that Cr is rapidly gettered and outdiffuses during normal alloying at 350°C. It is presently thought that the low-temperature motion of Cr into alloy damage regions and Au thin film layers are responsible, in part, for the degradation of Au-Ge-Ni contacts on GaAs after low-temperature thermal aging. Additional experiments are presently being conducted to investigate the low-temperature motion of Cr in the presence of lattice damage.

Fabrication of FET device structures in VPE layers grown on pre-gettered substrates showed considerable improvements compared to devices fabricated on control substrates. It is of particular importance that no pre-screening (selection) tests were used and the improvements in device yield/wafer were noted independent of the quality of the starting substrate material when pre-gettering processes were used. Experiments are continuing to determine if the pre-gettering step can be adequately incorporated as a pre-processing procedure to produce routine improvements in GaAs device yield and performance.

## REFERENCES

1. S. Dash, in Semiconductor Silicon, 1973, Electrochem. Soc., Princeton, N.J., p. 626 (1973).
2. J. E. Lawrence, in Semiconductor Silicon, Electrochem. Soc., Princeton, N.J., P. 596 (1969).
3. T. M. Buck, K. A. Pickar, J. M. Pate and C. M. Hsieh, Appl. Phys. Lett. 21, 485 (1972).
4. T. E. Seidel, R. L. Meek and A. G. Cullis, in Lattice Defects in Semiconductors, Inst. Phys., London, p. 494 (1975).
5. T. E. Seidel, R. L. Meek and A. G. Cullis, J. Appl. Phys. 46, 600 (1975).
6. H. J. Geipel and W. K. Tice, Appl. Phys. Lett. 7, 325 (1977).
7. T. J. Magee, J. Peng and J. D. Hong, Phys. Stat. Sol. (A) 55, 161 (1979).
8. T. J. Magee, J. Peng and J. D. Hong, ARPA (ONR) Contract Report (N00014-78-C-0065), Sept. 1978 (unpublished), ARACOR Technical Report 19-6, Dec. 1978).
9. T. Sigmon and C. A. Evans, Jr. (unpublished data).
10. T. Notaki, M. Ogawa, H. Terao and H. Watanabe in Gallium Arsenide and Related Compunds, 1974 (Inst. of Phys., London, 1975).
11. B. Tuck, G. A. Adegboyega, P. R. Jay and M. J. Cardwell in Gallium Arsenide and Related Compounds, 1978 (Inst. of Phys., London).
12. T. J. Magee, J. Peng, J. D. Hong, C. A. Evans, Jr, and V. R. Deline, Phys. Stat. Solidi (A) 55, 169 (1979).
13. G. H. Schwuttke and K. H. Yang, Final Rpt. ONR Contract No. N00173-76-C-0303, 1978.
14. C. O. Bozler, J. P. Donnelly, W. T. Lindley and R. A. Reynolds, Appl. Phys. Lett. 29, 698 (1976).
15. A. Lidow, J. F. Gibbons, T. Magee and J. Peng, J. Appl. Phys. 49, 5213 (1978).
16. N. Braslaw, J. B. Gunn, and J. L. Staples, Solid State Electron. 10, 381 (1967).
17. J. S. Harris, Y. Nannichi, G. L. Pearson, and G. F. Day, J. Appl. Phys. 40, 4575 (1969).



18. S. Knight and C. Paola, in Ohmic Contacts to Semiconductors, edited by B. Schwartz (Electrochemical Society, N. Y., 1969), p. 102
19. W. D. Edwards, W. A. Hartman, and A. B. Torrens, Solid State Electron.
20. K. Heime, U. Konig, E. Kohn, and A. Wortmann, Solid State Electron..
21. G. Y. Robinson, Solid State Electron. 18 331 (1975).
22. B. R. Pruneaux, J. Appl. Phys. 42, 3575 (1971).
23. H. Paria and H. Hartnagel, Appl. Phys. 10, 97 (1976).
24. J. Gyulai, J. W. Mayer, V. Rodriquez, A. Y. C. Yu, and H. J. Gopen, J. Appl. Phys. 42, 3578 (1971).
25. M. Wittmer, R. Pretorios, J. W. Mayer, and M. A. Nicolet, Solid State Electron, 20, 433 (1977).
26. D. A. Abbott and J. A. Turner, IEEE Trans. Microwave Theory Tech. MTT24, 317 (1976).
27. T. Irie, I. Nagasako, H. Kohzu, and K. Sekido, IEEE Trans. Microwave Theory Tech. MTT24, 321 (1976).
28. R. H. Cox and T. E. Hasty, in Ohmic Contacts to Semiconductors, edited by B. Schwartz (Electrochemical Society, New York, 1969), p. 88.
29. T. J. Magee, J. Peng, J. D. Hong, C. A. Evans, Jr., V. R. Deline, and R. M. Malbon, Appl. Phys. Lett. 35, 277 (1979).
30. C. A. Evans, Jr., V. R. Deline, T. W. Sigmon, and A. Lidow, Appl. Phys. Lett. 35 (1979).
31. A. K. Sinha and J. M. Poate, Appl. Phys. Lett. 23, 666 (1973).
32. T. J. Magee and J. Peng, Phys. Status. Solidi, A 32, 695 (1975).

DISTRIBUTION LIST - TECHNICAL REPORTS  
Contract N00014-78-C-0065

DARPA 1400 Wilson Blvd. Arlington, VA 22209 (Attn: Program Management)	2	Commanding Officer Office of Naval Research Branch Office 1030 East Green Street Pasadena, CA 91101
Office of Naval Research Code 427Y 800 North Quincy Street Arlington, VA 22217	4	Dr. M. Malbon/M.S. 1C Avantek, Inc. 3175 Bowers Avenue Santa Clara, CA 94304
Naval Research Laboratory 4555 Overlook Avenue, S.W. Washington, D.C. 20375 Attn: Code 2627 6800	6 1	Mr. R. Bierig Raytheon Company 28 Seyon Street Waltham, MA 02154
Office of Naval Research Branch Office 1030 East Green Street Pasadena, CA 91101	1	Dr. R. Bell, K-101 Varian Associates, Inc. 611 Hansen Way Palo Alto, CA 94304
TACIEC Battelle Memorial Institute 505 King Avenue Columbus, OH 43201	1	Dr. H. C. Nathanson Westinghouse Research and Development Center Beulah Road Pittsburgh, PA 15235
Defense Contract Administration Services Management Area San Francisco 1250 Bayhill Drive San Bruno, CA 94066	1	Dr. F. Blum/Dr. Daniel Chen Rockwell International Science Center P. O. Box 1085 Thousand Oaks, CA 91360
Defense Documentation Center Building 5, Cameron Station Alexandria, VA 22314		Mr. G. J. Gilbert MSC 100 Schoolhouse Road Somerset, NJ 08873
Dr. Y. S. Park AFAL/DHR Building 450 Wright-Patterson AFB Ohio 45433		Dr. C. Krumm Hughes Research Laboratory 3011 Malibu Canyon Road Malibu, CA 90265
ERADCOM DELET-M Fort Monmouth, NJ 07703		Mr. Lothar Wandinger ECOM/AMSEL/TL/1J Fort Monmouth, NJ 07003
Texas Instruments M.S. 105/W. Wisseman P. O. Box 5936 Dallas, TX 75222		

Dr. Harry Wieder  
Naval Ocean Systems Center  
Code 922  
271 Catalina Blvd.  
San Diego, CA 92152

Dr. William Lindley  
MIT  
Lincoln Laboratory  
F124A, P. O. Box 73  
Lexington, MA 02173

Mr. Sven Roosild  
AFCRL/LQD  
Hanscom AFB, MA 01731

Commander  
U.S. Army Electronics Command  
V. Gelnovatch  
(DRSEL-TL-IC)  
Fort Monmouth, NJ 07703

RCA  
Microwave Technology Center  
Dr. F. Sterzer  
Princeton, NJ 08540

Hewlett-Packard Corporation  
Dr. Robert Archer  
1501 Page Mill Road  
Palo Alto, CA 94306

Watkins-Johnson Company  
E. J. Crescenzi, Jr./  
K. Niclas  
3333 Hillview Avenue  
Stanford Industrial Park  
Palo Alto, CA 94304

Commandant  
Marine Corps  
Scientific Advisor (Code AX)  
Washington, D.C. 20380

Communications Transistor Corp.  
Dr. W. Weisenberger  
301 Industrial Way  
San Carlos, CA 94070

Microwave Associates  
Northwest Industrial Park  
Drs. F. A. Brand/J. Saloom  
Burlington, MA 01803

Commander, AFAL  
AFAL/DHM  
Mr. Richard L. Remski  
Wright-Patterson AFB, OH 45433

Professor Walter Ku  
Phillips Hall  
Cornell University  
Ithaca, NY 14853

Commander  
Harry Diamond Laboratories  
Mr. Horst W. A. Gerlach  
2800 Powder Mill Road  
Adelphia, MD 20783

Advisory Group on Electron  
Devices  
201 Varick Street, 9th floor  
New York, NY 10014

D. Claxton  
MS/1414  
TRW Systems  
One Space Park  
Redondo Beach, CA 90278

Professor L. Eastman  
Phillips Hall  
Cornell University  
Ithaca, NY 14853

AIL TECH  
612 N. Mary Avenue  
Sunnyvale, CA 94086  
Attn: D. G. Vendelin

Professors Hauser and Littlejohn  
Department of Electrical Engr.  
North Carolina State University  
Raleigh, NC 27607